

# INFLUENCE OF CHROMIUM CONTENT IN TEMPERING STEELS ON PHASE TRANSITION TEMPERATURE $A_1$ AND $A_3$ .

Zygmunt Żmuda<sup>1</sup>

## SUMMARY

For the three species of quenched and tempered steel (C50, 50Cr3, 51Cr6) dilatometric studies were conducted. They allowed the determination of transition temperatures  $Ac_1$  and  $Ac_3$  during heating and  $Ar_3$  and  $Ar_1$  during cooling. It was observed that increased the chromium content in steels tested resulted in an increase in transition temperature for heating and cooling. It was also observed narrow range of temperature from the beginning to the end of the transition with increasing chromium content.

**Keywords:** phase transitions, heat treatable steels, dilatometer tests, alloying elements

## ADMISSION

### Phase transition in low carbon steel

Both the eutectoid transformation of austenite to pearlite and pearlite to austenite called  $A_1$  and  $A_3$  allotropic transformation associated with the secretion of ferrite from austenite in carbon steels are important in the heat treatment. Precise temperature setting these changes in heating and cooling, it is important to choose the appropriate parameters for heat treatment of steel.

Alloying elements occurring in structural steel and tempering machine temperature changes cause changes. Some of the elements cause the temperature changes  $A_1$  and  $A_3$ , the other will decrease the temperature, a certain increase in temperature causes a reduction in the transformation temperature while the other transition [1]. Most of the alloying elements dissolved in austenite and therefore Ti, Mo, Si, W, Cr give rise eutectoid reaction temperature and only Mn and Ni cause the reduction. In turn, the lower the temperature changes affect allotropic alloying elements such as Cr, Mn, Ni, Cu, Pt, Au, C, N and the temperature elevation changes affect allotropic such as Co, Al, Si, W, Mo, V and Ti [2].

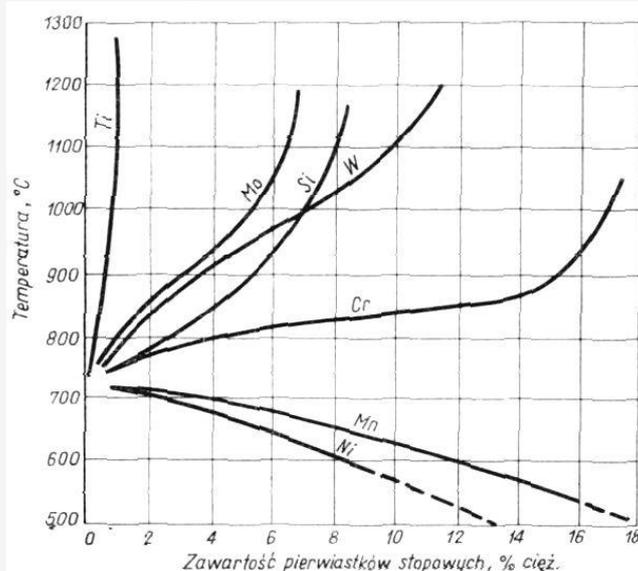


Figure 1. Effect of alloying elements on the eutectoid transformation temperature [1]

In addition, alloying elements are two ways to affect the stability of the austenite. Some elements e.g. Mn, Ni, Cu, Pt, Au, Co extended field of gamma phase. Another elements e.g. Al, Si, W, V, Ti, Cr narrowed gamma phase field.

<sup>1</sup> Zygmunt Żmuda, PhD Eng. Technical Institute, Jan Grodek State Vocational Academy in Sanok, ul. Mickiewicza 21, 38-500 Sanok, Poland, e-mail: . zygmuntzmuda@gmail.com

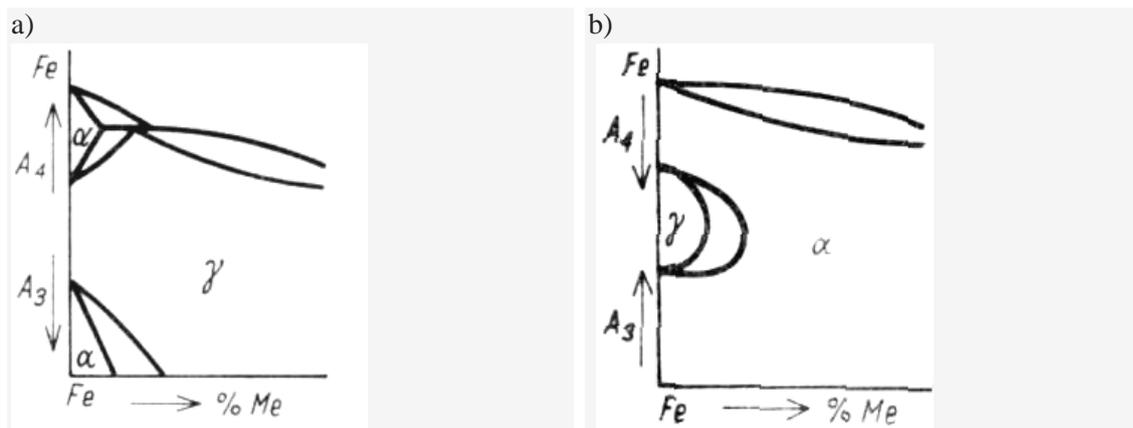


Figure 2. Influence alloying components on the stabilization of the gamma phase [1]

### Analysis of the chemical composition of the tested materials

The tests were three types of steel having similar carbon content and a varying chromium content. The test materials were subjected to analysis of chemical composition by using arc spark spectrometer PMI - MASTER PRO. The study confirmed the compliance of average concentrations of elements with the following standards: PN - EN 10250 - 3: 2001, PN - EN 10297 - 1: 2003, BS - EN 10305 - 1: 2003. The results are given in Table 1.

Table 1. The chemical composition of the tested materials.

Material	Content %				
	C	Cr	Mn	Si	Fe
C50	0,51	0,063	0,7	0,43	rest
50Cr3	0,50	0,810	0,8	0,40	rest
51Cr6	0,52	1,660	0,65	0,37	rest

### Dilatometer tests

To determine the allotropic transformation temperatures and phase are used dilatometric tests. In these studies utilizes the phenomenon of thermal expansion. Changes in volume of metals and alloys under the influence of temperature changes caused by the interatomic distances. As the temperature increases the amplitude of oscillation around a medium position carbon balance in the crystal lattice. The reconstruction of the allotropic transformation and the associated abrupt change of interatomic distances in the transition temperature cause a significant change in the dimensions of the test body. When the phase change (occurring in a certain temperature range) – on the dilatometric graph (Figure 3) the temperature of the beginning and end of the transformation are reflected by the collapse of the curves obtained upon heating and cooling of the sample.

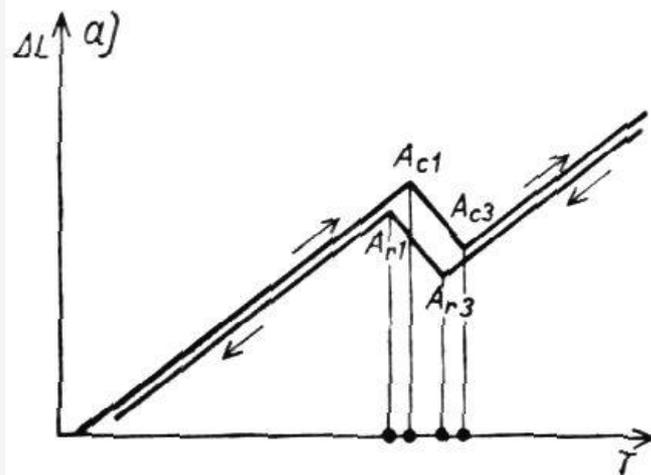


Figure 3. Schematic dilatometer curve for low carbon steel [3]

The study used an automatic dilatometer DA-3. Edited program allowed to conduct tests on the changes of temperature from ambient temperature to a temperature of 1000°C with different rates of heating and cooling. In clinical samples were used in the shape of a cylinder with a diameter of 6 mm and a length of 40mm. In Figure 4 presents the program conducted dilatometer tests.

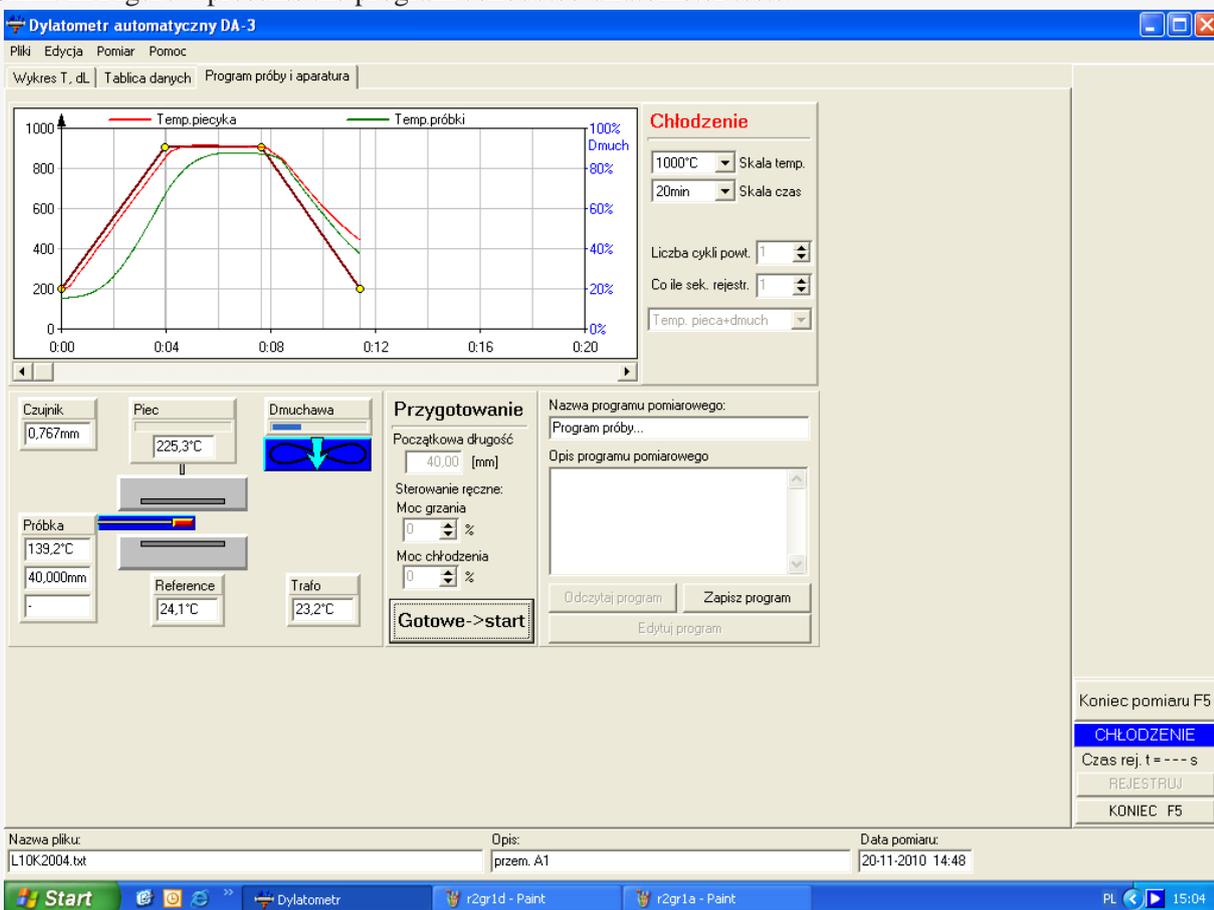


Figure 4. The dilatometer tests program.

## DILATOMETER TEST RESULTS AND ANALYSIS

Each test material was 5-fold sample heating and cooling. The resulting graphs allow the determination of temperature changes  $Ac_1$ ,  $Ac_3$ ,  $Ar_3$  and  $Ar_1$ . Method of determining these temperatures is shown in Figure 6. The calculated average temperature of transition showed in Table 2.

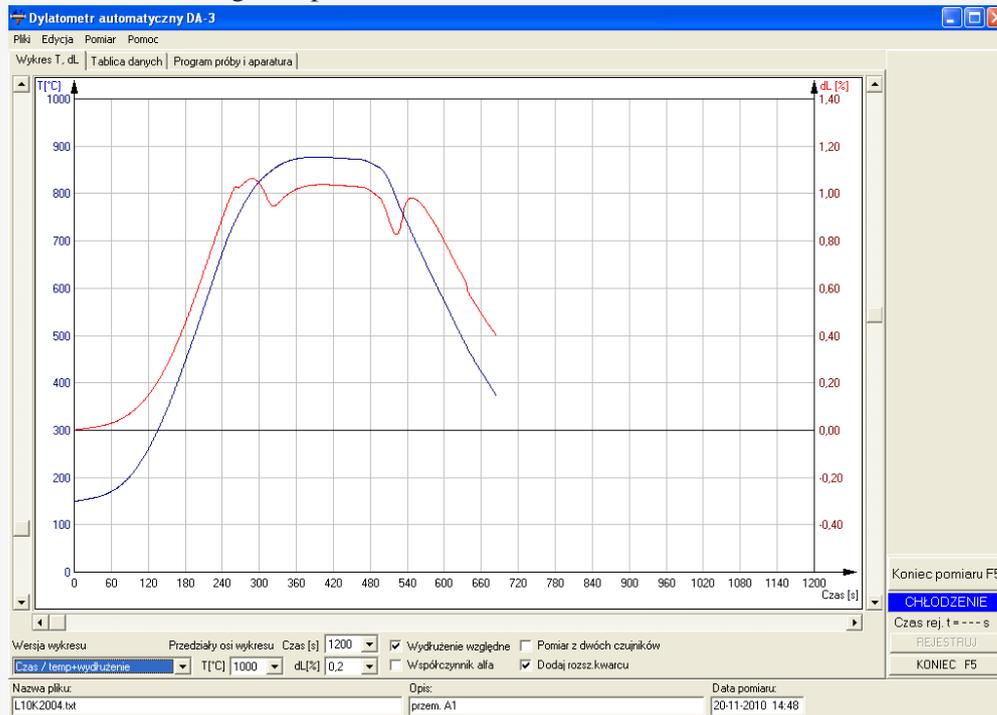


Figure 5. Graph of temperature and the length of the samples as a function of time.

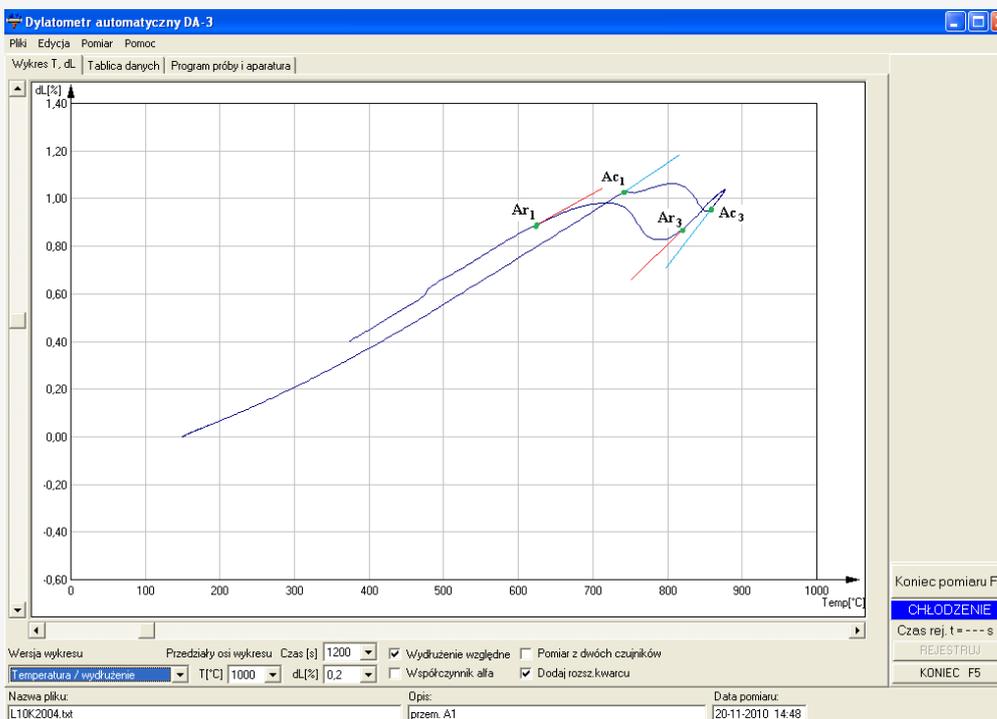


Figure 6. Figure sample length changes depending on the temperature and the method of determining the transition temperature.

Table 2. Average temperature of transition.

Material	temp. Ac <sub>1</sub>	temp. Ac <sub>3</sub>	temp. Ar <sub>3</sub>	temp. Ar <sub>1</sub>
	°C			
<b>C50</b>	741	870	801	652
<b>50Cr3</b>	745	866	792	660
<b>51Cr6</b>	760	859	785	665

In the studied material carbon, manganese and silicon was at a very similar level and only the chromium content varied significantly. Therefore, different transition temperatures in different materials must be attributed to the variable factor. Eutectoid transformation temperature A<sub>1</sub>, both when heating and cooling were increased with increasing chromium content. However, A<sub>3</sub> transition temperature during heating and cooling during decreased. Furthermore, it was observed that increased chromium content in steels cause narrowing of the temperature range from the beginning A<sub>1</sub> transformation to the end of A<sub>3</sub> transformation in heating and also reduce the range of temperature from the beginning A<sub>3</sub> transformation to the end of A<sub>1</sub> transformation during cooling. This was probably due to the fact that chromium eutectoid point moves to lower carbon content in the steel and thus steel containing 0.5 % carbon and increased chromium content has a structure similar to the eutectoid. As a result, the range of changes in temperature between A<sub>1</sub> and A<sub>3</sub> is reduced.

### References

- [1] Staub F., Adamczyk J., Cieślak Ł., Gubała J., Maciejny A.: Metaloznawstwo, Śląskie Wyd. Techniczne, Katowice, 1994.
- [2] Dobrzański L.: Metalowe materiały inżynierskie, Wyd. Naukowo-Techniczne, Warszawa, 2004.
- [3] Dobrzański L.: Metaloznawstwo z podstawami nauki o materiałach, Wyd. Naukowo-Techniczne, Warszawa, 1999.
- [4] Adamczyk J.: Inżynieria wyrobów stalowych, Wyd. Politechniki Śląskiej, Gliwice, 2000.
- [5] Butnicki S.: Spawalność i kruchość stali, Wyd. Naukowo-Techniczne, Warszawa, 1991.
- [6] Adamczyk J.: Metaloznawstwo teoretyczne, Wyd. Politechniki Śląskiej, Gliwice, 1999.
- [7] Dobrzański L.: Metaloznawstwo i obróbka cieplna stopów metali, Wyd. Politechniki Śląskiej, Gliwice, 1995.
- [8] Malkiewicz T.: Metaloznawstwo stopów żelaza, PWN, Warszawa-Kraków, 1978.
- [9] Przybyłowicz K.: Podstawy teoretyczne metaloznawstwa, Wyd. Naukowo-Techniczne, Warszawa, 1999.
- [10] Rudnik S.: Metaloznawstwo, PWN, Warszawa, 1994.
- [11] Wesołowski K.: Metaloznawstwo i obróbka cieplna, Wyd. Naukowo-Techniczne, Warszawa, 1978.